


**Please cite the Published Version**

Adlhart, C, Verran, J , Azevedo, NF, Olmez, H, Keinänen-Toivola, MM, Gouveia, I, Melo, LF and Crijns, F (2018) Surface modifications for antimicrobial effects in the healthcare setting: a critical overview. *Journal of Hospital Infection*, 99 (3). pp. 239-249. ISSN 0195-6701

**DOI:** <https://doi.org/10.1016/j.jhin.2018.01.018>

**Publisher:** Elsevier

**Version:** Published Version

**Downloaded from:** <https://e-space.mmu.ac.uk/628026/>

**Usage rights:**  [Creative Commons: Attribution-Noncommercial-No Derivative Works 4.0](https://creativecommons.org/licenses/by-nc-nd/4.0/)

**Additional Information:** This is an Open Access article published in *Journal of Hospital Infection*.

**Enquiries:**

If you have questions about this document, contact [openresearch@mmu.ac.uk](mailto:openresearch@mmu.ac.uk). Please include the URL of the record in e-space. If you believe that your, or a third party's rights have been compromised through this document please see our Take Down policy (available from <https://www.mmu.ac.uk/library/using-the-library/policies-and-guidelines>)



## Review

# Surface modifications for antimicrobial effects in the healthcare setting: a critical overview

C. Adlhart<sup>a</sup>, J. Verran<sup>b</sup>, N.F. Azevedo<sup>c</sup>, H. Olmez<sup>d</sup>, M.M. Keinänen-Toivola<sup>e</sup>,  
I. Gouveia<sup>f</sup>, L.F. Melo<sup>c,\*</sup>, F. Crijns<sup>g</sup>

<sup>a</sup> Institute of Chemistry and Biotechnology, Zurich University of Applied Sciences ZHAW, Wädenswil, Switzerland

<sup>b</sup> School of Healthcare Science, Manchester Metropolitan University, Manchester, UK

<sup>c</sup> University of Porto, Faculty of Engineering, LEPAE, Portugal

<sup>d</sup> TÜBİTAK MAM, Materials Institute, 3B Center, Gebze, Turkey

<sup>e</sup> Satakunta University of Applied Sciences, Faculty of Technology, Rauma, Finland

<sup>f</sup> FibEnTech – Fiber Materials and Environmental Technologies, Research Unit, Faculty of Engineering, University of Beira Interior, Portugal

<sup>g</sup> Zuyd University of Applied Sciences, Heerlen, The Netherlands

## ARTICLE INFO

**Article history:**

Received 27 November 2017

Accepted 25 January 2018

Available online 2 February 2018

**Keywords:**

Healthcare contamination

Antimicrobial coatings

Safe-by-design



## SUMMARY

The spread of infections in healthcare environments is a persistent and growing problem in most countries, aggravated by the development of microbial resistance to antibiotics and disinfectants. In addition to indwelling medical devices (e.g. implants, catheters), such infections may also result from adhesion of microbes either to external solid–water interfaces such as shower caps, taps, drains, etc., or to external solid–gas interfaces such as door handles, clothes, curtains, computer keyboards, etc. The latter are the main focus of the present work, where an overview of antimicrobial coatings for such applications is presented. This review addresses well-established and novel methodologies, including chemical and physical functional modification of surfaces to reduce microbial contamination, as well as the potential risks associated with the implementation of such anti-contamination measures. Different chemistry-based approaches are discussed, for instance anti-adhesive surfaces (e.g. superhydrophobic, zwitterions), contact-killing surfaces (e.g. polymer brushes, phages), and biocide-releasing surfaces (e.g. triggered release, quorum sensing-based systems). The review also assesses the impact of topographical modifications at distinct dimensions (micrometre and nanometre orders of magnitude) and the importance of applying safe-by-design criteria (e.g. toxicity, contribution for unwanted acquisition of antimicrobial resistance, long-term stability) when developing and implementing antimicrobial surfaces.

© 2018 The Author(s). Published by Elsevier Ltd  
on behalf of The Healthcare Infection Society. This is an open access article  
under the CC BY-NC-ND license (<http://creativecommons.org/licenses/by-nc-nd/4.0/>).

## Introduction

Infections and infectious diseases are a continuous threat to human health. According to the European Centre for Disease Prevention and Control, more than four million people are

\* Corresponding author. Address: Universidade do Porto Faculdade de Engenharia, Chemical Engineering, Rua Dr. Roberto Frias, s/n, Porto, 4200-265, Portugal. Tel.: +35 1225081588; fax: +35 1225081449.

E-mail address: [lmelo@fe.up.pt](mailto:lmelo@fe.up.pt) (L.F. Melo).

estimated to acquire a healthcare-associated infection (HCAI) every year in Europe (1.7 million in the USA) [1]. The number of deaths occurring as a direct consequence of these infections is estimated to be at least 37,000, and these infections are thought to contribute indirectly to an additional 110,000 deaths each year (in the USA, a total of 99,000 deaths is estimated).

The present review does not deal with indwelling medical devices. It is mostly focused on solid–air interfaces in health-care units, such as tables, door-handles, computer keyboards, textiles, although solid–liquid surfaces are also of great concern in hospitals such as taps, showers and drains, where biofilms appear frequently. New methods, in addition or as an alternative to appropriate use of disinfectants and antibiotics, are required to reduce microbial activity, associated infections and to reverse the increase in antimicrobial resistance. A potential and promising weapon against bacterial growth and possibly the development of multidrug-resistant bacteria has been found in antimicrobial (nano)coatings (AMC) [2,3].

A state-of-the-art innovation to combat pathogenic bacteria is the creation of self-disinfecting surfaces through the application of coatings with antibiofouling and/or bactericidal properties. Bactericidal coatings are interesting in healthcare because of the capability of these coatings to kill pathogens upon contact. Many different chemical strategies and technologies for antibacterial coatings are described in the literature. For instance, antibacterial coatings may contain active eluting agents (e.g. ions or nanoparticles of silver, copper, zinc, or antibiotics, chloride, iodine), immobilized molecules that become active upon contact (e.g. quaternary ammonium polymers or peptides), or light-activated molecules (e.g. TiO<sub>2</sub> or photosensitizers) [4–6].

In addition to chemical modifications, the topography of a surface can by itself significantly affect its hygienic status, either in a beneficial manner (reducing microbial retention) or otherwise (increasing retention) [7]. As such, modifications of surfaces to enhance antimicrobial properties should always take into account the effect of surface wear on subsequent fouling and cleanability. Therefore, efforts should be undertaken to characterize typical wear, assess interactions with the most likely micro-organisms in that environment, and define the most appropriate and least damaging cleaning and sanitizer regimes. The best way to achieve such outcomes is to ensure that multidisciplinary expertise is integrated into developmental processes, and that testing methods are appropriately robust [8].

A relevant aspect of the surfaces is that they should be safe-by-design (SbD). In a broad sense, SbD is the elimination of the potential health and safety risks associated with a product or process by taking into account those potential risks during the early design phase. SbD is a generic concept with an ultimate goal of obtaining a product that complies with all regulations by designing out the health and safety risks that can be more difficult or sometimes impossible to deal with in the long-term after the market introduction. The SbD approach is not new in industry and has been used for many years under different names by the construction industry, aircraft industry, railway industry, etc. [9]. This opinion paper starts by assessing the different types of strategy to chemically modify the surfaces and by identifying potentially new strategies, followed by discussions on the impact of topography and the importance of the SbD approach.


## Methods

Through its Cooperation in Science and Technology programme (COST), the European Commission has recently funded a four-year initiative to establish a network of stakeholders involved in development, regulation, and use of novel antimicrobial coatings for prevention of HCAI [10]. The network AMiCI (AntiMicrobial Coating Innovations) currently comprises participants of more than 60 universities, research institutes and companies across 30 European countries ([www.amici-consortium.eu](http://www.amici-consortium.eu)) and, to date, represents the most comprehensive grouping to target the use of these emergent technologies in healthcare settings. Within AMiCI, one of the working groups is collecting information on commercially available antimicrobial coatings with actual or potential application in healthcare, and the development of new coatings that are SbD. This review article is the result of extensive discussion within the working group and the AMiCI consortium as a whole, following the 'world café approach' [11].

For the identification of relevant publications, a literature search was performed in SciFinder and PubMed of studies published between 2000 and 2017. The following search terms were used, coupled with the keywords 'surface' OR 'coating': 'antimicrobial', 'antibacterial', 'functionalized', 'safe-by-design', 'topography AND (microorganism OR bacteria)', 'contact active', 'anti-adhesive', and 'biocide release'. Due to the high number of studies identified, each of the publications was then assessed for its suitability and relevance of the findings to the topic of the present review. A few publications that were not identified in the previous search, but that were known to the authors as cornerstone studies in the field of surface modifications in healthcare settings, were also included.

## Chemical modifications to achieve functional antimicrobial coatings

Strategies to achieve antimicrobial coatings can be classified according to their functional principle as: (i) anti-adhesive, (ii) contact active, and (iii) biocide release (Figure 1). Whereas the first two principles may be considered as SbD, biocide release incorporates the release of a toxic substance and can therefore be considered as toxic by design. Sometimes two functional principles are combined to achieve synergistic effects, e.g. by embedding biocidal substances into anti-adhesive surfaces. Today, the majority of chemical modifications includes hydrogels or poly(ethylene glycol) (PEG) to repel approaching microbes, metals (in particular, silver and copper), antimicrobial peptides (AMPs), quaternary ammonium compounds (QACs), and nanoparticles [13–18]. Beyond those established approaches, state-of-the-art or potentially new strategies towards antimicrobial coatings were identified at the AMiCI meetings and were sorted and classified according to their functional principle. For many of the latest antimicrobial strategies, the mechanism of antimicrobial activity is still under investigation and there is not enough information available on whether antimicrobial activity happens directly at the surface or whether small amounts of active compounds are released into the test media where they will exert their antimicrobial activity, or whether both mechanisms are acting in parallel.

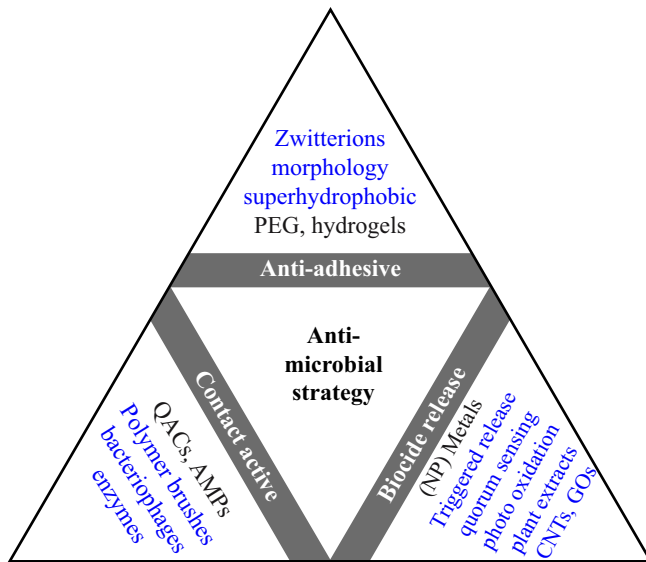

**Figure 1.** Established (black) and potentially upcoming strategies (blue) for antimicrobial coatings classified by their functional principle. The functional principle is also a matter of implementation, e.g. QACs are active both chemically bound to a surface and in solution. Results from the AMiCI meeting. Carbon nanotubes (CNTs), graphene(oxide)s (GOs), poly(ethylene glycol) (PEG) quaternary ammonium compounds (QACs), antimicrobial proteins peptides (AMPs), nanoparticle (NP).

### Anti-adhesive surfaces

Anti-adhesive surfaces can reduce the adhesion force between bacteria and a solid surface to enable the easy removal of bacteria before a biofilm layer is formed on the surface [19]. Such surfaces may suppress HCAI by blocking transmission paths involving surfaces, but they will not reduce the number of germs on the contacting media by killing them. Attachment of bacteria or cells starts with an initial adsorption of proteins on to the material surface [20]. Strategies to prevent protein attachment include superhydrophobic surfaces, often augmented by a hierarchical nanostructure as well as zwitterionic polymers [19,21].

Superhydrophobic surfaces are characterized by a water contact angle  $>150^\circ$  and they are inspired by the lotus leaf in nature [22]. It was further revealed that the lotus leaf has a hierarchical micro/nanostructure [23]. Reducing bacterial adhesion via superhydrophobicity is a relatively new topic and has yet to be studied thoroughly and systematically [19]. Analysis of superhydrophobic siloxane and fluorosiloxane surfaces showed also minimal protein adsorption, both before and after protein adsorption trials [24].

Nanostructures are important, since effective air entrapment in the three-dimensional nanomorphology (nanopillars) renders them superhydrophobic and slippery. On inherently nanostructured hydrophilic aluminium, adhesion forces of bacteria were reduced by a factor of 4 down to 2–4 nN compared to the electropolished flat surface, resulting in an 88% reduction of colony-forming units (cfu) for *Staphylococcus aureus*. This effect was even more pronounced after applying a hydrophobic Teflon coating, yielding a 99.9% reduction under flow conditions [25].

Nanostructured surfaces were also prepared using electrospun polystyrene nanofibres. When oxygen plasma-treated, a superhydrophilic surface was generated, which exhibited limited *Escherichia coli* attachment due to negative zeta potential of  $-40$  mV. After fluorination, a superhydrophobic surface was obtained, which exhibited self-cleaning ability against bacteria, where the initially adhered bacteria were effectively removed with subsequent washing [26]. Anti-adhesion and killing was achieved by combining an upper superhydrophobic surface layer (silane coated poly(acrylic acid)) with limited bacterial adhesion and self-cleaning properties with a hydrophilic bottom layer (poly(ethyleneimine)– $\text{Ag}^+$  complex) which could deliver bactericidal silver ions [27].

An interesting anti-adhesive and killing approach is found in nature. The nanopatterned cicada wing surface uses an adsorption and stretching mechanism with eventual rupture. As the bacterial cells adsorb on to the nanopillared structures present on the wing surfaces, the bacterial cell membrane stretches in the regions suspended between the pillars. If the degree of stretching is sufficient, cell rupture will occur [28].

Zwitterionic polymer brushes may also delay or even prevent microbial attachment to a surface, since the hydration layer surrounding the ionic surface prevents non-specific protein adsorption [21]. Using barnacle cement, a biological adhesive from barnacles, and ‘click’ chemistry, poly(2-(methacryloyloxy)ethyl trimethylammonium chloride) polymer brushes were successfully attached to stainless steel and antimicrobial properties were demonstrated [21]. Zwitterionic polymer brushes cannot inactivate bacterial cells. Therefore, synergistic anti-adhesion and bacterial inactivation was achieved by grafting zwitterionic poly(sulfobetaine methacrylate) brushes with embedded biocidal silver nanoparticles [29]. The importance of anti-adhesive properties for biofilm formation was also demonstrated by measuring the adhesive forces on brush-coated silicone rubber and uncoated silicon rubber. On the brush-coated rubber, adhesion was so weak that the bacteria were no longer able to sense the surface and therefore remained in their planktonic state, susceptible to antibiotics rather than forming a protected biofilm [30].

### Contact-active surfaces

Contact-active surfaces exhibit antimicrobial activity without releasing biocidal substances. Several mechanisms are believed to take place in contact-active surfaces [31]. These are: (i) a so-called spacer effect, where the biocidal group is attached to the surface through a polymer chain, allowing the biocide to reach the cytoplasmic membrane of the bacteria and to perforate them; (ii) alternatively, positively charged QACs, e.g. 3-aminopropyl trimethoxysilane grafted to cellulose nanofibres, can detach phospholipids from the cell membrane and thereby kill the bacteria [32–34]. This approach is also referred to as biomimetic with respect to the activity of chitosan – a polysaccharide derived from exoskeleton of crustaceans or cell walls of fungi. Hydrophobic parts of a surface can act similarly to QACs by deforming the membrane through adhesion [35].

Polymer brushes have been widely used in preparing contact-active antimicrobial surfaces without biocidal release. The rationale behind polymer brushes is the observation that antimicrobial molecules lose much of their activity, once attached to a surface. When providing an anchor for the active



molecule through a flexible covalently bound polymeric chain, the active molecule should still be able to reach the site of action at or within the bacterium, e.g. by penetrating its cell wall, but leaching is still suppressed. Important parameters for polymer brush anchors are chain length and chain density. Polymer brushes have been shown to be effective for anchoring QACs or AMPs [36–40]. Using surface-initiated atom transfer radical polymerization, QACs with charge densities of  $>1.5 \times 10^{15}$  accessible quaternary amine units/cm<sup>2</sup> were anchored through poly-2-(dimethylamino)ethyl methacrylate chains. Interestingly, these surfaces were bioactive even though the polymer chains were too short to penetrate the cells with envelope thicknesses of 46 nm for Gram-negative *E. coli* and 45.55 nm for Gram-positive *Bacillus subtilis* [36]. This demonstrates that surface charge density can be more important than chain length. On the other hand, it was clearly shown that *N*-alkyl-pyridinium exhibited high antimicrobial activity when anchored through a 750 or 25 kDa polyethyleneimine (PEI) but showed no activity when using the 2 kDa analogue [37]. Therefore, only long-chained, moderately hydrophobic immobilized polycations exhibit microbicidal activity. Interestingly, polycationic polymer brushes are not subject to existing mechanisms of resistance such as multidrug-resistance pumps or multidrug tolerance protein-expressing cells, presumably since there are no analogue structures in nature [37].

Polymer brushes have also successfully been used for anchoring AMPs. AMPs are a logical alternative to conventional antibiotics due to their broad-spectrum antimicrobial activities [38]. Surface concentrations of AMPs up to 5.9 µg/cm<sup>2</sup> were achieved by conjugating the peptides to surface-immobilized primary amine functionalized polymer chains obtained by aqueous surface-initiated atom transfer radical polymerization of *N,N*-dimethylacrylamide and aminopropyl methacrylamide hydrochloride [38]. The efficacy of AMPs attached to catheter material surface using polymer brushes was verified *in vivo* by using a catheter-associated urinary tract infection mouse model [39]. By adding arginine–glycine–aspartate peptides to promote host-tissue cell adhesion to AMPs anchored through the block copolymer Pluronic F-127, two effects were achieved, namely thwarting bacteria from approaching and attaching to the surface and, simultaneously, enhancing tissue integration [40].

A completely different approach is given by immobilizing bacteriophages on surfaces [41]. Bacteriophages are viruses that infect bacteria and are highly efficient and relatively cost-effective. Bacteriophages are host specific, but they can have a broad host range, infecting several strains or species of bacteria, both Gram-positive and Gram-negative. They proved to be efficient in preventing bacterial contamination and recently they became accepted for food treatment to counter food contamination during storage. In addition, the fact that the EU is contributing €3.8 million to the Phagoburn study shows that it is willing to consider the approach [42]. Attachment of bacteriophages to a surface can be achieved through physisorption, electrostatic attachment, and covalent bonding [43]. Sample surfaces, which exhibited antimicrobial activities with immobilized phages, included gold, glass, cellulose membrane, and hydrogels [44–47]. Phages are specifically sensitive to moisture and can be deactivated when dried. However, reactivation upon wetting is feasible, and addition of polysaccharides improves their stability [43].

Two other groups of naturally occurring antimicrobials are claimed as alternatives to antibiotics: bacterial cell wall hydrolases (BCWHs) and antimicrobial peptides [48]. Antimicrobial peptides have a broad-spectrum against bacteria and fungus, low level of induced resistance, but may cause toxicity at high doses in order to be efficient and are more costly to produce. BCWHs have limitations towards Gram-negative bacteria, due to the presence of the outer membrane, and some important Gram-positive pathogens such as *S. aureus* are already resistant to lysozymes.

### Biocide-releasing surfaces

Biocide-releasing surfaces may have some conceptual disadvantages since they are toxic by design in terms of releasing biocidal substances. In addition they will gradually become inactive and they may induce the formation of resistance [31]. Catalytically active surfaces, such as photocatalytically active surfaces (e.g. TiO<sub>2</sub>) which regenerate reactive oxygen species upon UV radiation, provide an alternative.

Another approach is triggered release depending on certain threshold concentrations of quorum-sensing molecules which are found in biofilms [49,50].

Surface coating with carbon nanotubes (CNTs), graphene or diamond-like carbons (DLCs) promised interesting antimicrobial activity, since these materials show relatively low cytotoxicity towards mammalian cells. Whether these materials are active on the surface or whether they achieve antimicrobial activity through releasing traces into the aqueous phase is not yet resolved, but their activity in microbial suspensions is clearly demonstrated, e.g. higher toxicity is found for surfactant-dispersed CNTs [51]. The most frequently proposed mechanisms of action fall under four categories: (i) oxidative stress induction, (ii) protein dysfunction, (iii) membrane damage, and (iv) transcriptional arrest [52]. Recently, it was also demonstrated that the mechanism of action depends on the concentration of the bactericide – in this case graphene oxide (GO): low GO concentrations cut membranes of the micro-organisms *S. aureus* and *E. coli* whereas high concentrations induce the formation of GO aggregates shielding their edges. When cluster size increases, bacterial deactivation through wrapping is observed [53].

Graphene-based materials differ in their morphology (mono and multilayers) as well as in their surface chemistry (graphene, GO, reduced graphene oxide (rGO)). Lateral size for instance is important to enhance bacterial adhesion whereas the sharp edges may act as nanoknives. GOs can enhance the antimicrobial activity through oxidative stress with or without the production of reactive oxygen species [54]. When comparing the antibacterial activity of graphite, graphite oxide, GO, and rGO towards *E. coli* under similar conditions, GO showed the highest antibacterial activity, followed by rGO, graphite, and graphite oxide [51]. Synergistic effects are reported for graphene-based silver nanocomposites and composites with other antibacterial nanoparticles, as well as with polymeric or enzymatic bactericides [55].

Carbon nanotubes have also been widely studied as antimicrobial material since they can be easily embedded into polymers. Again, a variety of morphologies has been studied such as single wall or multi-wall, but it seems that GO-based materials show higher antimicrobial activity [56]. Synergistic effects were obtained by making composites of CNTs and

chitosan within a hydrogel, or by decorating CNTs with poly(amidoamine)dendrimer-immobilized CDs and Ag<sub>2</sub>S quantum dots which enhanced the antimicrobial activity in solution [57,58]. CNTs can also be used to prepare antimicrobial coatings either by electrodeposition of a polyvinyl-*N*-carbazole–CNT film or by preparing spin-coated films [59]. In the same work, the antimicrobial activity of dispersed CNTs was studied and it was found that such antimicrobial activity depended on the degree of dispersions. Antimicrobial activity of CNTs depends also on the length of CNTs, as was shown for poly(lactic-co-glycolic acid)-embedded CNTs, where the shorter ones were more active [60].

Diamond-like carbons represent a further morphology of carbon materials. In contrast to graphite, graphene and CNTs, tetrahedrally structured amorphous carbons with C–C sp<sup>3</sup> bonding are dominating with a significant amount of C–H bonds. They can be prepared by chemical vapour deposition, e.g. on stainless steel surfaces, and they can be doped with known antimicrobial metals such as copper, silver, or platinum [61]. When comparing the antimicrobial activity of pure DLCs and germanium-doped DLCs, significant reduction in *Pseudomonas aeruginosa* biofilm formation was observed whereas these surface films showed no effect against Gram-positive *S. aureus* biofilms [61].

Carbon quantum dots (CDs) are a relatively new class of carbon materials which can be used for bacterial identification due to their tunable photoluminescence properties. CDs exhibit low toxicity and appreciable biocompatibility [62]. When decorating the surface of CDs with QACs or Ag NPs, it was possible to selectively attach C-dots to Gram-positive bacteria and to induce antimicrobial activity through the membrane-disrupting mechanism [62,63].

Photocatalytic oxidation is a possible alternative strategy for antimicrobial coatings in the hospital environment [64]. Due to the self-regenerating biocidal effect of the catalytically released reactive oxygen species, such surfaces remain active throughout their lifetime. Many of the reported surfaces contain the photocatalyst TiO<sub>2</sub>, which generates highly active OH-radicals in the presence of water, oxygen, and UV-A light. These highly reactive OH-radicals are able to destroy bacteria [65]. Current research is focusing on shifting the photocatalytic activity of such coatings towards the visible light range, e.g. by adding silver nanoparticles which can act through their surface plasmon resonance effects, or molybdenum [66,67]. When incorporating a combination of photosensitive dyes such as Crystal Violet with the inherently antimicrobial ZnO nanoparticles into polymer surfaces, synergistic photocatalytic antimicrobial activity was reported. The polymers exhibited significant bacterial kills using typical white light sources of hospital environments within 1 h against Gram-positive bacteria and within 6 h against Gram-negative bacteria [68]. By combining a dye with Ag nanoparticles, bactericidal activity of the Ag nanoparticles could be enhanced under white light illumination. It is believed that the enhancement effect is due to an increase in bactericidal activity through the triplet state of the dye by biomolecular reaction rather than by enhancement of the concentration of reactive oxygen species [69].

Surfaces decorated with metal oxide Lewis acids such as MoO<sub>3</sub> or WO<sub>3</sub> have also shown a broad-band antimicrobial activity [70]. Their mechanism of action is based on the in-situ generation of H<sub>3</sub>O<sup>+</sup> ions through the reaction with moisture from the air [71,72]. The resulting acidified surfaces have a pH

of 4.5–5.5 and the H<sub>3</sub>O<sup>+</sup> ions are able to diffuse through the cell membranes where they can distort the pH-equilibrium and transport systems of the cell [72,73].

Reduced toxicity and prolonged durability of the antimicrobial effect may also be achieved by the triggered release of biocidal molecules. Recent strategies are based on quorum sensing: quorum-sensing molecules (e.g. homoserine lactones for Gram-negative bacteria) enable bacteria to detect the presence of other bacteria and to communicate with them [74]. The concentration of quorum-sensing molecules increases with bacterial multiplication and at certain threshold concentrations the expression of many genes is affected, such as genes encoding for adhesion or lipases, which are particularly abundant at sites of infection [75,76]. By coupling the antibiotic ciprofloxacin through a lipase-sensitive homoserine group on to the surface of a PEG model compound, a self-regulating system was obtained [75]. Alternatively, anti-quorum sensing enzymes could prevent bacteria from forming biofilms by suppressing the quorum-sensing molecule concentration below the threshold value [74].

Many plant extracts are well known for their antimicrobial properties and much research is devoted to their application to protect food from pathogens [77]. However, limited research has been done on investigating their efficacy on surfaces of healthcare units or on medical devices, such as tympanostomy tubes [78]. It has been shown that a tea-tree oil coating may induce zones of inhibition against MRSA after a two-day incubation [79].

## Impact of topography on surface effectiveness

It is generally acknowledged that defects or design features on any inert surface can retain soil and/or micro-organisms, and therefore affect cleanliness, disinfection, and hygienic status of the surface. Implications in the clinical environment in terms of cross-infection control, the choice of surface material to be used, and the cleaning and sanitization protocols are significant.

However, the assumption ‘the rougher the surface, the worse the hygienic status’ is somewhat simplistic, although many publications make this type of claim. Cells are easily removed from ‘smooth’ surfaces, but they may be retained within features approximating in size to that of the cells. In larger features, the cells may again be relatively easily removed. Typically, surface topography is measured by the *R<sub>a</sub>*-value, defined as ‘the average departure of the surface profile from a center line’. Other parameters are also used, but the *R<sub>a</sub>*-value is the most popular in the microbiology literature. An *R<sub>a</sub>*-value of 0.8 μm is often deemed indicative of a hygienic surface. In profilometry, a trace is taken of the surface, typically perpendicular to the lay of the surface features, using a probe. However, the probe will itself vary in size, depending on the method used to assess topography, from solid stylus, through laser scanning to the nanoscale tip of the atomic force microscope (which generates *R<sub>a</sub>*-values in nanometers). The resolution of these different probes will affect the result obtained, although, using standardized surfaces of different degrees of roughness, the ranking (if not the absolute measurement) would likely be the same irrespective of the method used. In addition, the profilometer might reveal a two- or three-dimensional impression of the surface. If two-dimensional, then the overall picture

of the surface is not revealed: a feature identified along a linear trace might indicate a scratch or a pit – the type as well as degree of roughness may be important in terms of microbial retention. Three-dimensional images are more valuable, for example revealing very different topographies for surfaces with comparable  $R_a$ -values.

Since the  $R_a$ -value is a statistical measure, then the actual feature size, or the variation in feature size across a surface, is not revealed. This may be important if features of the dimension of microbial cells are present within larger features, with macro-, micro- and nano-features each potentially having different effects on the retention of cells on the surface. Indeed, the previously mentioned 'lotus effect' reveals that a hierarchical micro/nanostructure can significantly reduce retention, enabling cells to 'roll off' the surface. The fabrication of surfaces with well-defined nano-topographies provides a new avenue for the design of anti-adhesive/easily cleanable (and therefore hygienic) surfaces – depending on the intended environment of use [80,81].

The environment in which surfaces are placed will also affect their hygienic status. At a flowing solid–liquid interface, cells will move across the surface, and may be retained in features where they may replicate and form biofilms with accompanying 'streamers' which may detach and contaminate downstream [82]. This is a particular issue with joints in pipework. However, on open surfaces, at a solid–air interface, the cells tend to be deposited on the surface through contact with vectors such as food, fingers, equipment, or splashing [83]. In this case, replication is less likely, since water availability is low, and the survival of cells on these surfaces is key to maintaining hygienic status [84]. Antimicrobial surfaces, and/or surfaces which are hard or difficult to abrade, coupled with effective cleaning regimes, are strategies employed to counter this phenomenon. The continued cleaning/soiling cycle can itself affect the surface, causing abrasions that result in increased soiling and require increasing force in cleaning – which in turn may increase abrasion. The nature of the surface itself can affect how it wears: steel and other metals tend to scratch; glass and ceramics tend to fracture; softer materials such as plastics will abrade more easily.

Antimicrobial surfaces that actively leach out active agents might prove more effective if the surface area is increased through abrasion, but the presence of retained organic material (blood, food, sputum) in addition to micro-organisms might impede the antimicrobial effect and protect the microbial cells. It might be argued that the increase in surface area presented by surfaces with increased roughness is the driver for the increased retention – but this has not been convincingly proven. The features themselves, in terms of shape, profile, and size clearly provide an increased area of contact for cells, enhancing their ability to remain on surfaces [85]. All of these issues should be considered when developing novel and effective antimicrobial surfaces, focusing on minimizing wear to maintain cleanliness and cleanability.

At the cellular level, several studies focus on the retention of cells on surfaces. The typical experiment involves the incubation of surface with cell suspension for a specified time-period (such as 1 h), rinsing and removal prior to staining retained cells, and quantifying the amount of retention (cell numbers per unit area, or area of microscopic field covered by cells). However, one might debate which is more desirable: high numbers of retained cells which are easily removed, in comparison to low numbers of


retained cells which resist detachment. Here, issues of cell survival and inactivation are also important.

The atomic force microscope is one means of assessing the strength of attachment of cells on a surface. The probe scans repeatedly across the surface, moving vertically in response to surface features. This movement is captured and imaged using lasers. By increasing the force of the scan, less strongly attached cells are removed. Thus the strength of attachment as well as the amount of retention can be assessed [85]. This work has revealed that the size of cells and their relationship with the feature size affect strength of attachment: as might be expected, comparable feature size and cell size is the least desirable combination, enabling maximum contact area between cell and surface. In addition, cell shape will also affect this interaction, with rod-shaped cells having a larger area of contact available for interaction with the cell surface in comparison to cocci. Investigation of the strength of attachment of cells on linear features where the force is applied either across or along the feature has revealed different results: demonstrating easier removal along well-defined features on titanium-coated stainless steel, but easier removal by applying force across features on softer polymeric surfaces [86,87]. As noted above, this work has led to the fabrication of surfaces with designed topographies that are targeted at inhibiting attachment of particular cells, where surface features smaller than cells might reduce their ability to strongly attach to the surface, and therefore improve cleanability (Figure 2). The robustness of these surfaces is essential to ensuring a long-lasting effect, and the potentially interfering effect of organic material must also be considered.

When considering open surfaces that are usually present at a solid–air interface, which is the main focus of this paper, biofilms are of less concern. In the clinical/medical environment, high-touch surfaces (worktops, walls, door-handles, telephones, patient surrounds) are the prime focus for antimicrobial treatments and/or effective cleaning. Solid–liquid interfaces, where biofilms could form, would likely be encountered around taps, showers or drains. The topography of the surface underlying the biofilm does not necessarily influence the quantity of the biofilm itself – again depending on the scale of feature size – but after cleaning, the substratum will retain cells in features which can regrow and reduce the time taken for the biofilm to develop once more.

## Importance of safe-by-design in antimicrobial coatings

Application of the SbD approach for AMC that are based on chemicals and nanomaterials is more challenging compared to

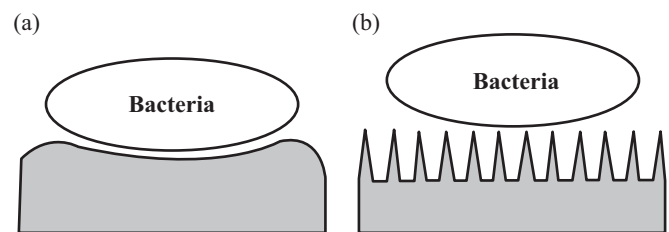

**Figure 2.** (a) Micron-sized features may favour bacterial adhesion, whereas (b) nano-sized features may create difficult topographic conditions for attachment.

those based on other types of materials, since usually there are neither standard test protocols nor enough data on the toxicity, absorption, metabolism, excretion, accumulation and bio-persistence of these antimicrobial agents (especially of the nanomaterials), nor on their penetration into biological barriers both at an environmental level and mammalian cell level. EU programmes such as NanoFase, SafeNano, ProSafe, NaNo-Reg, and Euro-NanoTox aim to allow the early assessment of the toxicity and fate of nanomaterials with a strategy to establish and implement standardized toxicological measurement, establish international standards and to provide centralized nanotoxicology information (Figure 3).

There are four main challenges in designing safe AMC: (i) the toxicity of the materials used; (ii) the potential impact of the antimicrobial agent on the development of antimicrobial resistance; (iii) the durability of the antimicrobial activity in the long term (the long-term stability); (iv) the lack of standardized methods for testing the performance of the AMCs under representative environmental conditions, namely their antimicrobial efficacy and long-term stability.

Silver is the dominant type of antimicrobial agent used in AMCs, followed by zinc oxide, zirconium, zinc omadine, titanium dioxide, quaternary ammonia compounds. The current AMC market mainly relies on the antimicrobial metal nanoparticles. Therefore, when talking about the toxicity of AMCs, metallic nanoparticles – mainly nano-silver – are the main subject. The environmental persistence and toxicity of biocides and antimicrobial nanomaterials represent a potential health and environmental issue. This may create a dilemma in the attempt to control HCAI through antimicrobial strategies. Because these antimicrobial strategies are employed to kill/control bacteria while they pose the risk of spreading, assessment is required for less known, less traceable and controllable nanoparticles with hardly understood mechanisms of action, toxicity and fate in the environment as well as within the body. One of the goals of the AMiCl group is to join forces to tackle such issues.

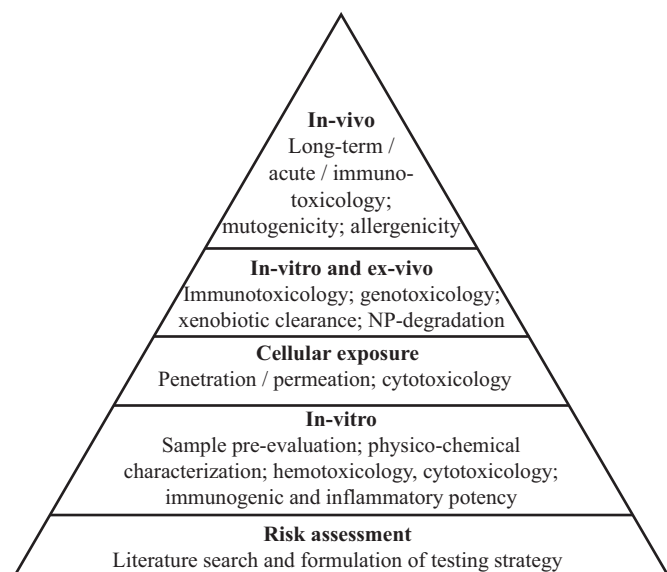


Figure 3. Multi-level Euro-NanoTox strategy. NP, nanoparticle. Adapted from Falk [12].

Mankind discovered the existence of one-celled microscopic creatures in the 1670s following the studies of Leeuwenhoek. Then it took almost 260 years to discover the first antibiotic for the control of bacteria, but much longer to develop techniques for the detection, monitoring and identification of bacteria in various environments. We are now equipped with advanced technology tools that enable us to detect and identify bacteria in minutes or even in seconds with 'standardized methods', as well as with many antibacterial agents effective in killing and controlling bacteria. However, it is hard to say that the human race won the fight against bacteria, as it is obvious that many of the agents discovered and used against bacteria resulted in the evolution of bacteria into much more resistant forms. Experts in this field and the Centers for Disease Control and Prevention define this problem as a 'nightmare' and an 'apocalyptic threat' for the human race. Although, shortly after his discovery of penicillin in 1928, Alexander Fleming warned about the development of antimicrobial resistance, it was not until the 2000s that outcomes of antibiotic resistance were clearly understood and large-scale official actions have been started. The difficulty in preventing the spread of antibiotic resistance stems from the widespread dissemination of antibiotics, and thus antibiotic resistance develops in a wide range of environments including hospitals, agriculture and food, community, soil, water resources and associated sites. Therefore, the development and implementation of SbD strategies is a key issue for the development of future generations of coatings for healthcare environments, such as nano-antimicrobial-based AMCs. An important requisite of AMCs is thus to minimize the risk of development of another 'apocalyptic threat' due to the spread of biocides and antimicrobial nanomaterials and the potential development of associated antimicrobial resistance and other toxicity issues while trying to control and prevent HCAI. Taking into account our current ability to detect, identify and monitor the nanoparticles and to extend our knowledge on the mechanisms of action, toxicity and fate of these nanoparticles in various environments, this might end up with a worst scenario.

An in-depth analysis of the toxicity and persistence of nano-antimicrobials in the environment is necessary to assess the safety of AMCs within the context of SbD. The rationale behind adding an antimicrobial agent to a specific surface should be balance between the potential impact of the antimicrobial agent on the emergence of resistant microbial strains and the impact of preventing the spread of the pathogenic microbial strains within the healthcare environment, and thus on the control of HCAI [88]. Several strategies have been employed to produce SbD reduced toxicity antimicrobial nanomaterials [89,90]. It is found that the concentration of nanoparticles to which the cells are exposed, the type of surface coating, the nature and extent of doping, and the aspect ratio of the particles make significant contributions to the cell toxicity of the nanoparticles [91]. Recent studies showed that Fe-doping is a possible safe design strategy for preventing ZnO toxicity in animals and the environment [92,93]. Moreover, polymer coating and modification with poly ethylene glycol (PEG) reduces the toxicity and cellular uptake of silver nanoparticles (Ag NPs) [94].

The time and cost constraints of the toxicity assessment methods represent another challenge for toxicity assessment of the nano-antimicrobials used in AMCs. Predictive nanotoxicology models appear as a feasible alternative for toxicity assessment [95].



The potential impact of AMCs on the development of antimicrobial resistance is a challenge that should be taken into serious consideration. Although the prevalence is still low, silver-resistant bacterial strains were found in hospital sewage systems [96]. Studies revealed the risk of both co- and cross-resistance to antibiotics and antimicrobials used in AMCs (biocides and metals) [97,98]. Therefore, these metal-based antimicrobials might contribute to the maintenance and spread of antibiotic resistance factors. Sütterlin *et al.* reported that silver resistance genes are widely represented in clinical isolates of the genera *Enterobacter* and *Klebsiella* in Swedish healthcare facilities [99]. Therefore, to avoid further selection and spread of silver-resistant bacteria with high potential for healthcare-associated infections, the use of silver-based products needs to be controlled and the silver resistance monitored.

Antimicrobial efficacy and long-term stability against the standard hygiene and sanitation protocols implemented in healthcare facilities are the main performance criteria for the AMCs aimed at reducing HCAI in healthcare facilities. Failure or weakness in the rigorous assessment of the coatings may result in unreliable performance. The lack of standard protocols for assessing the antimicrobial efficacy and long-term stability of the AMCs represents another challenge, which makes it impossible to establish a proper comparison between AMCs with different antimicrobial agents and processing technologies that are both in the market and in the R&D phase. In fact, issues with demonstration of functionality, efficacy, toxicity and potential risk of antimicrobial resistance development are one of the main market restraints for the commercialization of AMCs [10].

## Conclusions

As mentioned above, an effective antimicrobial coating must achieve a multitude of characteristics: (i) be able to control the pathogenic population of a surface; (ii) be stable (mechanically, tribologically and chemically) in the wide range of hospital settings; (iii) minimize (eco)toxicological hazards and risks of antimicrobial resistance emergence; (iv) be affordable and easily implemented. Future technological developments should hence aim at tackling most, if not all, of these points. The ultimate goal of the antimicrobial coating, namely the prevention of thousands of deaths occurring as a direct consequence of HCAI in healthcare facilities, cannot be tackled by the coating alone. But a tremendous common effort involving coating technology providers, clinical and cleaning staff as well as the responsible handling of antibiotics – to name merely the clinical and agricultural sectors among many others – is required.

Regarding the ability to control the pathogenic population of a surface, very promising strategies have emerged. One of these is widely known as selective killing, or the ability of antimicrobial surfaces to target only those species that are deemed to cause a risk to patients or hospital staff. Strategies such as the use of quorum sensing at a threshold concentration to release an antimicrobial compound have recently appeared. Others, such as the modulation of the colonization consortia as a whole to inhibit the dominance of pathogens, in a strategy similar to the one used to control the human microbiome, should start appearing as microbial ecological concepts are better deciphered.

Depending on their intended use, antimicrobial surfaces will be challenged by a number of factors. For instance, door handles are in intermittent contact with hands, but nonetheless are not expected to be exposed to as much wear as bed linens, that should be washed on a daily basis. Studies on the weariness or robustness of the different materials under different conditions are available, but they require further methodological standardization to allow for a more meaningful interpretation of the results.

Biocidal chemicals used in antimicrobial coatings are inherently toxic; biocide-releasing surfaces are subjected to the Biocidal Products Regulation (BPR, Regulation (EU) 528/2012) and by the Regulation (EC) No. 1907/2006 of the European Parliament and of the Council on the Registration, Evaluation, Authorization and Restriction of Chemicals (REACH). This regulatory barrier makes it very expensive and time-consuming to bring antimicrobial coatings, of which the antimicrobial activity is related to biocidal release, to the market. On the other hand, anti-adhesive surfaces can be considered as SbD since there are no biocidal molecules involved which may either induce toxic effects or lead to the evolution of resistance. In this respect, the control of specific surface topography characteristics, in conjugation with chemically based strategies and specific cleaning protocols, could lead to a novel generation of improved SbD products.

Overall, the novel strategies that are continuously being developed in the area of nanosurfaces bring some hope to the field of antimicrobial control, while decreasing microbial resistance to antibiotics and associated infections in clinical settings. It is then crucial to provide suitable standardized assessment tests and a fast transition of these strategies from the lab bench to the market, by conjugating efforts between academia and industry.

## Acknowledgements

This article is based upon work from COST Action AMiCI (CA15114), supported by COST (European Cooperation in Science and Technology).

### Conflict of interest statement

None declared.

### Funding sources

This work was financially supported by: Project POCI-01-0145-FEDER-006939 (Laboratory for Process Engineering, Environment, Biotechnology and Energy (LEPABE)) funded by FEDER funds through COMPETE2020 – Programa Operacional Competitividade e Internacionalização (POCI), and by national funds through FCT (Fundação para a Ciência e a Tecnologia).

## References

- [1] European Centre for Disease Prevention and Control. Point prevalence survey of healthcare-associated infections and antimicrobial use in European acute care hospitals 2011–2012. Stockholm: ECDC; 2013.
- [2] Page K, Wilson M, Parkin IP. Antimicrobial surfaces and their potential in reducing the role of the inanimate environment in the incidence of hospital-acquired infections. *J Mater Chem* 2009;19:3819–31.

- [3] Crijns FR, Keinanen-Toivola MM, Dunne CP. Antimicrobial coating innovations to prevent healthcare-associated infection. *J Hosp Infect* 2017;95:243–4.
- [4] Chen X, Hirt H, Li Y, Gorr SU, Aparicio C. Antimicrobial GL13K peptide coatings killed and ruptured the wall of *Streptococcus gordonii* and prevented formation and growth of biofilms. *PLoS One* 2014;9:e111579.
- [5] Grass G, Rensing C, Solioz M. Metallic copper as an antimicrobial surface. *Appl Environ Microbiol* 2011;77:1541–7.
- [6] Dizaj SM, Lotfipour F, Barzegar-Jalali M, Zarrintan MH, Adibkia K. Antimicrobial activity of the metals and metal oxide nanoparticles. *Mater Sci Eng C Mater Biol Appl* 2014;44:278–84.
- [7] Whitehead KA, Verran J. The effect of surface topography on the retention of microorganisms. *Food Bioprocess Processing* 2006;84:253–9.
- [8] Ojeil M, Jermann C, Holah J, Denyer SP, Maillard JY. Evaluation of new in vitro efficacy test for antimicrobial surface activity reflecting UK hospital conditions. *J Hosp Infect* 2013;85:274–81.
- [9] Hochwimmer A, de Kretser A. Safety by Design Processes for the Engineering of Geothermal Facilities. Proceedings World Geothermal Congress. Melbourne, Australia, 19–25 April 2015.
- [10] Dunne CP, Keinanen-Toivola MM, Kahru A, Teunissen B, Olmez H, Gouveia I, et al. Anti-microbial coating innovations to prevent infectious diseases (AMiCI): cost action ca15114. *Bioengineered* 2017;8:679–85.
- [11] Brown J, Isaacs D. The world café: shaping our futures through conversations that matter. San Francisco: Berrett-Koehler; 2005.
- [12] Falk A. Assessment of toxicological effects by in vitro and in vivo assays and open flow microperfusion. 4th ed. Euro-NanoTox-Letters; 2015. Available at: <https://www.nanosafetycluster.eu/eu-nanosafety-cluster-projects/national-projects/euro-nanotox.html> [last accessed February 2018].
- [13] Desai NP, Hossainy SF, Hubbell JA. Surface-immobilized polyethylene oxide for bacterial repellence. *Biomaterials* 1992;13:417–20.
- [14] Liu JY, Sonshine DA, Shervani S, Hurt RH. Controlled release of biologically active silver from nanosilver surfaces. *ACS Nano* 2010;4:6903–13.
- [15] Gomes AP, Mano JF, Queiroz JA, Gouveia IC. Incorporation of antimicrobial peptides on functionalized cotton gauzes for medical applications. *Carbohydr Polym* 2015;127:451–61.
- [16] Pedrosa M, Mouro C, Nogueira F, Vaz J, Gouveia I. Comparison of the antibacterial activity of modified-cotton with magainin I and LL-37 with potential as wound-dressings. *J Appl Polymer Sci* 2014;131:8.
- [17] Gilbert P, Moore LE. Cationic antiseptics: diversity of action under a common epithet. *J Appl Microbiol* 2005;99:703–15.
- [18] Hasan J, Crawford RJ, Ivanova EP. Antibacterial surfaces: the quest for a new generation of biomaterials. *Trends Biotechnol* 2013;31:295–304.
- [19] Zhang X, Wang L, Levänen E. Superhydrophobic surfaces for the reduction of bacterial adhesion. *RSC Adv* 2013;3:12003.
- [20] Zhu H, Guo Z, Liu W. Adhesion behaviors on superhydrophobic surfaces. *Chem Commun (Camb)* 2014;50:3900–13.
- [21] Yang WJ, Cai T, Neoh KG, Kang ET, Teo SL, Rittschof D. Barnacle cement as surface anchor for ‘clicking’ of antifouling and antimicrobial polymer brushes on stainless steel. *Biomacromolecules* 2013;14:2041–51.
- [22] Yan YY, Gao N, Barthlott W. Mimicking natural superhydrophobic surfaces and grasping the wetting process: a review on recent progress in preparing superhydrophobic surfaces. *Adv Colloid Interface Sci* 2011;169:80–105.
- [23] Feng L, Li SH, Li YS, Li HJ, Zhang LJ, Zhai J, et al. Super-hydrophobic surfaces: from natural to artificial. *Adv Mater* 2002;14:1857–60.
- [24] Stallard CP, McDonnell KA, Onayemi OD, O’Gara JP, Dowling DP. Evaluation of protein adsorption on atmospheric plasma deposited coatings exhibiting superhydrophilic to superhydrophobic properties. *Biointerphases* 2012;7:31.
- [25] Hizal F, Rungraeng N, Lee J, Jun S, Busscher HJ, van der Mei HC, Choi CH. Nanoengineered superhydrophobic surfaces of aluminum with extremely low bacterial adhesivity. *ACS Appl Mater Interfaces* 2017;9:12118–29.
- [26] Yuan Y, Hays MP, Hardwidge PR, Kim J. Surface characteristics influencing bacterial adhesion to polymeric substrates. *RSC Adv* 2017;7:14254–61.
- [27] Shen L, Wang B, Wang J, Fu J, Picart C, Ji J. Asymmetric free-standing film with multifunctional anti-bacterial and self-cleaning properties. *ACS Appl Mater Interfaces* 2012;4:4476–83.
- [28] Pogodin S, Hasan J, Baulin VA, Webb HK, Truong VK, Phong Nguyen TH, et al. Biophysical model of bacterial cell interactions with nanopatterned cicada wing surfaces. *Biophys J* 2013;104:835–40.
- [29] Liu C, Faria AF, Ma J, Elimelech M. Mitigation of biofilm development on thin-film composite membranes functionalized with zwitterionic polymers and silver nanoparticles. *Environ Sci Technol* 2017;51:182–91.
- [30] Muszanska AK, Nejadnik MR, Chen Y, van den Heuvel ER, Busscher HJ, van der Mei HC, et al. Bacterial adhesion forces with substratum surfaces and the susceptibility of biofilms to antibiotics. *Antimicrob Agents Chemother* 2012;56:4961–4.
- [31] Krumm C, Tiller JC. Kontaktaktiv oder durch Biozide. *Nachrichten aus der Chemie* 2014;62:984–7.
- [32] Tiller JC, Liao CJ, Lewis K, Klibanov AM. Designing surfaces that kill bacteria on contact. *Proc Natl Acad Sci USA* 2001;98:5981–5.
- [33] Saini S, Belgacem MN, Salon M-CB, Bras J. Non leaching biomimetic antimicrobial surfaces via surface functionalisation of cellulose nanofibers with aminosilane. *Cellulose* 2016;23:795–810.
- [34] Bieser AM, Tiller JC. Mechanistic considerations on contact-active antimicrobial surfaces with controlled functional group densities. *Macromol Biosci* 2011;11:526–34.
- [35] Asri LATW, Crismaru M, Roest S, Chen Y, Ivashenko O, Rudolf P, et al. A shape-adaptive, antibacterial-coating of immobilized quaternary-ammonium compounds tethered on hyperbranched polyurea and its mechanism of action. *Adv Funct Mater* 2014;24:346–55.
- [36] Murata H, Koepsel RR, Matyjaszewski K, Russell AJ. Permanent, non-leaching antibacterial surface – 2: how high density cationic surfaces kill bacterial cells. *Biomaterials* 2007;28:4870–9.
- [37] Lewis K, Klibanov AM. Surpassing nature: rational design of sterile-surface materials. *Trends Biotechnol* 2005;23:343–8.
- [38] Gao G, Lange D, Hilpert K, Kindrachuk J, Zou Y, Cheng JT, et al. The biocompatibility and biofilm resistance of implant coatings based on hydrophilic polymer brushes conjugated with antimicrobial peptides. *Biomaterials* 2011;32:3899–909.
- [39] Yu K, Lo JC, Yan M, Yang X, Brooks DE, Hancock RE, et al. Anti-adhesive antimicrobial peptide coating prevents catheter associated infection in a mouse urinary infection model. *Biomaterials* 2017;116:69–81.
- [40] Muszanska AK, Rochford ET, Gruszka A, Bastian AA, Busscher HJ, Norde W, et al. Antiadhesive polymer brush coating functionalized with antimicrobial and RGD peptides to reduce biofilm formation and enhance tissue integration. *Biomacromolecules* 2014;15:2019–26.
- [41] Melo LD, Veiga P, Cerca N, Kropinski AM, Almeida C, Azeredo J, et al. Development of a phage cocktail to control *Proteus mirabilis* catheter-associated urinary tract infections. *Front Microbiol* 2016;7:1024.
- [42] Reardon S. Phage therapy gets revitalized. *Nature* 2014;510:15–16.
- [43] Hosseinidou Z, Olsson AL, Tufenkji N. Going viral: designing bioactive surfaces with bacteriophage. *Colloids Surf B Biointerfaces* 2014;124:2–16.
- [44] Tawil N, Sacher E, Mandeville R, Meunier M. Strategies for the immobilization of bacteriophages on gold surfaces monitored by

- surface plasmon resonance and surface morphology. *J Phys Chem C* 2013;117:6686–91.
- [45] Hosseini Z, Van de Ven TG, Tufenkji N. Bacterial capture efficiency and antimicrobial activity of phage-functionalized model surfaces. *Langmuir* 2011;27:5472–80.
- [46] Anany H, Chen W, Pelton R, Griffiths MW. Biocontrol of *Listeria monocytogenes* and *Escherichia coli* O157:H7 in meat by using phages immobilized on modified cellulose membranes. *Appl Environ Microbiol* 2011;77:6379–87.
- [47] Fu W, Forster T, Mayer O, Curtin JJ, Lehman SM, Donlan RM. Bacteriophage cocktail for the prevention of biofilm formation by *Pseudomonas aeruginosa* on catheters in an in vitro model system. *Antimicrob Agents Chemother* 2010;54:397–404.
- [48] Parisien A, Allain B, Zhang J, Mandeville R, Lan CQ. Novel alternatives to antibiotics: bacteriophages, bacterial cell wall hydrolases, and antimicrobial peptides. *J Appl Microbiol* 2008;104:1–13.
- [49] Defoirdt T, Boon N, Bossier P, Verstraete W. Disruption of bacterial quorum sensing: an unexplored strategy to fight infections in aquaculture. *Aquaculture* 2004;240:69–88.
- [50] Ramage G, Saville SP, Wickes BL, López-Ribot JL. Inhibition of *Candida albicans* biofilm formation by farnesol, a quorum-sensing molecule. *Appl Environ Microbiol* 2002;68:5459–63.
- [51] Liu SB, Zeng TH, Hofmann M, Burcombe E, Wei J, Jiang RR, et al. Antibacterial activity of graphite, graphite oxide, graphene oxide, and reduced graphene oxide: membrane and oxidative stress. *ACS Nano* 2011;5:6971–80.
- [52] Rojas-Andrade MD, Chata G, Rouholiman D, Liu J, Saltikov C, Chen S. Antibacterial mechanisms of graphene-based composite nanomaterials. *Nanoscale* 2017;9:994–1006.
- [53] Palmieri V, Bugli F, Lauriola MC, Cacaci M, Torelli R, Ciasca G, et al. Bacteria meet graphene: modulation of graphene oxide nanosheet interaction with human pathogens for effective antimicrobial therapy. *ACS Biomater Sci Engng* 2017;3:619–27.
- [54] Zou X, Zhang L, Wang Z, Luo Y. Mechanisms of the antimicrobial activities of graphene materials. *J Am Chem Soc* 2016;138:2064–77.
- [55] Zhu J, Wang J, Hou J, Zhang Y, Liu J, Van der Bruggen B. Graphene-based antimicrobial polymeric membranes: a review. *J Mater Chem A* 2017;5:6776–93.
- [56] Chang Y-N, Gong J-L, Zeng G-M, Ou X-M, Song B, Guo M, et al. Antimicrobial behavior comparison and antimicrobial mechanism of silver coated carbon nanocomposites. *Process Safety Environ Protect* 2016;102:596–605.
- [57] Venkatesan J, Jayakumar R, Mohandas A, Bhatnagar I, Kim S-K. Antimicrobial activity of chitosan–carbon nanotube hydrogels. *Materials* 2014;7:3946–55.
- [58] Neelgund GM, Oki A, Luo Z. Antimicrobial activity of CdS and Ag2S quantum dots immobilized on poly(amidoamine) grafted carbon nanotubes. *Colloids Surf B Biointerfaces* 2012;100:215–21.
- [59] Ahmed F, Santos CM, Vergara RA, Tria MC, Advincula R, Rodrigues DF. Antimicrobial applications of electroactive PVK-SWNT nanocomposites. *Environ Sci Technol* 2012;46:1804–10.
- [60] Aslan S, Loebick CZ, Kang S, Elimelech M, Pfefferle LD, Van Tassel PR. Antimicrobial biomaterials based on carbon nanotubes dispersed in poly(lactic-co-glycolic acid). *Nanoscale* 2010;2:1789–94.
- [61] Robertson SN, Gibson D, MacKay WG, Reid S, Williams C, Birney R. Investigation of the antimicrobial properties of modified multi-layer diamond-like carbon coatings on 316 stainless steel. *Surf Coatings Technol* 2017;314:72–8.
- [62] Jana J, Gauri SS, Ganguly M, Dey S, Pal T. Silver nanoparticle anchored carbon dots for improved sensing, catalytic and intriguing antimicrobial activity. *Dalton Trans* 2015;44:20692–707.
- [63] Yang J, Zhang X, Ma YH, Gao G, Chen X, Jia HR, et al. Carbon dot-based platform for simultaneous bacterial distinguishment and antibacterial applications. *ACS Appl Mater Interfaces* 2016;8:32170–81.
- [64] Abreu AC, Tavares RR, Borges A, Mergulhao F, Simoes M. Current and emergent strategies for disinfection of hospital environments. *J Antimicrob Chemother* 2013;68:2718–32.
- [65] Kühn KP, Chaberny IF, Massholder K, Stickler M, Benz VW, Sonntag H-G, et al. Disinfection of surfaces by photocatalytic oxidation with titanium dioxide and UVA light. *Chemosphere* 2003;53:71–7.
- [66] Dunnill CW, Page K, Aiken ZA, Noimark S, Hyett G, Kafizas A, et al. Nanoparticulate silver coated-titania thin films – photo-oxidative destruction of stearic acid under different light sources and antimicrobial effects under hospital lighting conditions. *J Photochem Photobiol A: Chem* 2011;220:113–23.
- [67] Fisher L, Ostovapour S, Kelly P, Whitehead KA, Cooke K, Storgårds E, et al. Molybdenum doped titanium dioxide photocatalytic coatings for use as hygienic surfaces: the effect of soiling on antimicrobial activity. *Biofouling* 2014;30:911–9.
- [68] Noimark S, Weiner J, Noor N, Allan E, Williams CK, Shaffer MSP, et al. Dual-mechanism antimicrobial polymer-ZnO nanoparticle and crystal violet-encapsulated silicone. *Adv Funct Mater* 2015;25:1367–73.
- [69] Hwang GB, Noimark S, Page K, Sehmi S, Macrobert AJ, Allan E, et al. White light-activated antimicrobial surfaces: effect of nanoparticles type on activity. *J Mater Chem B* 2016;4:2199–207.
- [70] Lackner M, Maninger S, Guggenbichler JP. Saure Oberflächen als neuartige Kontaktbiozide. *Nachr Chem* 2013;61:12–5.
- [71] Lorenz K, Bauer S, Gutbrod K, Guggenbichler JP, Schmuki P, Zollfrank C. Anodic TiO<sub>2</sub>(2) nanotube layers electrochemically filled with MoO<sub>3</sub>(3) and their antimicrobial properties. *Bio-interphases* 2011;6:16–21.
- [72] Zollfrank C, Gutbrod K, Wechsler P, Guggenbichler JP. Antimicrobial activity of transition metal acid MoO<sub>3</sub>(3) prevents microbial growth on material surfaces. *Mater Sci Eng C Mater Biol Appl* 2012;32:47–54.
- [73] Plumridge A, Hesse SJ, Watson AJ, Lowe KC, Stratford M, Archer DB. The weak acid preservative sorbic acid inhibits conidial germination and mycelial growth of *Aspergillus niger* through intracellular acidification. *Appl Environ Microbiol* 2004;70:3506–11.
- [74] Thallinger B, Prasetyo EN, Nyanhongo GS, Guebitz GM. Antimicrobial enzymes: an emerging strategy to fight microbes and microbial biofilms. *Biotechnol J* 2013;8:97–109.
- [75] Komnatny VV, Chiang WC, Tolker-Nielsen T, Givskov M, Nielsen TE. Bacteria-triggered release of antimicrobial agents. *Angew Chem Int Ed Engl* 2014;53:439–41.
- [76] Roland PL, Hans HL, Pierre CW, Rudolf LT. The targets of currently used antibacterial agents: lessons for drug discovery. *Curr Pharmaceut Design* 2007;13:3140–54.
- [77] Ponce AG, Roura SI, del Valle CE, Moreira MR. Antimicrobial and antioxidant activities of edible coatings enriched with natural plant extracts: in vitro and in vivo studies. *Postharvest Biol Technol* 2008;49:294–300.
- [78] Wang JC, Hamood AN, Saadeh C, Cunningham MJ, Yim MT, Cordero J. Strategies to prevent biofilm-based tympanostomy tube infections. *Int J Pediatr Otorhinolaryngol* 2014;78:1433–8.
- [79] Park H, Jang CH, Cho YB, Choi CH. Antibacterial effect of tea-tree oil on methicillin-resistant *Staphylococcus aureus* biofilm formation of the tympanostomy tube: an in vitro study. *In Vivo* 2007;21:1027–30.
- [80] Meng Q, Wang Z, Chai X, Weng Z, Ding R, Dong L. Fabrication of hematite ( $\alpha$ -Fe<sub>2</sub>O<sub>3</sub>) nanoparticles using electrochemical deposition. *Appl Surf Sci* 2016;368:303–8.
- [81] Kim P, Kreder MJ, Alvarenga J, Aizenberg J. Hierarchical or not? Effect of the length scale and hierarchy of the surface roughness on omniphobicity of lubricant-infused substrates. *Nano Lett* 2013;13:1793–9.

- [82] Whitehead KA, Verran J. Formation, architecture and functionality of microbial biofilms in the food industry. *Curr Opin Food Sci* 2015;2:84–91.
- [83] Verran J, Redfern J. Testing surface cleanability in food processing. 2nd ed. Oxford: Elsevier; 2016.
- [84] Redfern J, Verran J. Effect of humidity and temperature on the survival of *Listeria monocytogenes* on surfaces. *Lett Appl Microbiol* 2017;64:276–82.
- [85] Whitehead KA, Rogers D, Colligon J, Wright C, Verran J. Use of the atomic force microscope to determine the effect of substratum surface topography on the ease of bacterial removal. *Colloids Surf B Biointerfaces* 2006;51:44–53.
- [86] Verran J, Packer A, Kelly PJ, Whitehead KA. Use of the atomic force microscope to determine the strength of bacterial attachment to grooved surface features. *J Adhes Sci Technol* 2010;24:2271–85.
- [87] Verran J, Jackson S, Coulthwaite L, Scallan A, Loewy Z, Whitehead K. The effect of dentifrice abrasion on denture topography and the subsequent retention of microorganisms on abraded surfaces. *J Prosthet Dent* 2014;112:1513–22.
- [88] Ahonen M, Kahru A, Ivask A, Kasemets K, Koljalg S, Mantecca P, et al. Proactive approach for safe use of antimicrobial coatings in healthcare settings: opinion of the COST Action Network AMiCI. *Int J Environ Res Public Health* 2017;14.
- [89] Schulte PA, Geraci CL, Murashov V, Kuempel ED, Zumwalde RD, Castranova V, et al. Occupational safety and health criteria for responsible development of nanotechnology. *J Nanopart Res* 2014;16:2153.
- [90] Castranova V. Overview of current toxicological knowledge of engineered nanoparticles. *J Occup Environ Med* 2011;53. S14–17.
- [91] Le TC, Yin H, Chen R, Chen Y, Zhao L, Casey PS, et al. An experimental and computational approach to the development of ZnO nanoparticles that are safe by design. *Small* 2016;12:3568–77.
- [92] Xia T, Zhao Y, Sager T, George S, Pokhrel S, Li N, et al. Decreased dissolution of ZnO by iron doping yields nanoparticles with reduced toxicity in the rodent lung and zebrafish embryos. *ACS Nano* 2011;5:1223–35.
- [93] Naatz H, Lin S, Li R, Jiang W, Ji Z, Chang CH, et al. Safe-by-design CuO nanoparticles via Fe-doping, Cu-O bond length variation, and biological assessment in cells and zebrafish embryos. *ACS Nano* 2017;11:501–15.
- [94] Pang C, Brunelli A, Zhu C, Hristozov D, Liu Y, Semenzin E, et al. Demonstrating approaches to chemically modify the surface of Ag nanoparticles in order to influence their cytotoxicity and bio-distribution after single dose acute intravenous administration. *Nanotoxicology* 2016;10:129–39.
- [95] Brehm M, Kafka A, Bamler M, Kühne R, Schüürmann G, Sikk L, et al. An integrated data-driven strategy for safe-by-design nanoparticles: the FP7 MODERN project. *Adv Exp Med Biol* 2017;947:257–301.
- [96] Lima de Silva AA, de Carvalho MA, de Souza SA, Dias PM, da Silva Filho RG, de Meirelles Saramago CS, et al. Heavy metal tolerance (Cr, Ag AND Hg) in bacteria isolated from sewage. *Braz J Microbiol* 2012;43:1620–31.
- [97] Pal C, Asiani K, Arya S, Rensing C, Stekel DJ, Larsson DGJ, et al. Metal resistance and its association with antibiotic resistance. *Adv Microb Physiol* 2017;70:261–313.
- [98] Baker-Austin C, Wright MS, Stepanauskas R, McArthur JV. Co-selection of antibiotic and metal resistance. *Trends Microbiol* 2006;14:176–82.
- [99] Sutterlin S, Dahlo M, Tellgren-Roth C, Schaal W, Melhus A. High frequency of silver resistance genes in invasive isolates of *Enterobacter* and *Klebsiella* species. *J Hosp Infect* 2017;96:256–61.